

## Concrete Masonry


- CMU Production
- Size and Application
- Performance
- Calcium Silicate Units
- Glass Units
- Natural Stone Units
- Autoclaved Aeriated Concrete Units

Ennis House  
Frank Lloyd Wright  
1924




## Ennis House

- Los Angeles, Calif.
- Frank Lloyd Wright
- 1924
- Mayan Revival
- Textile Block

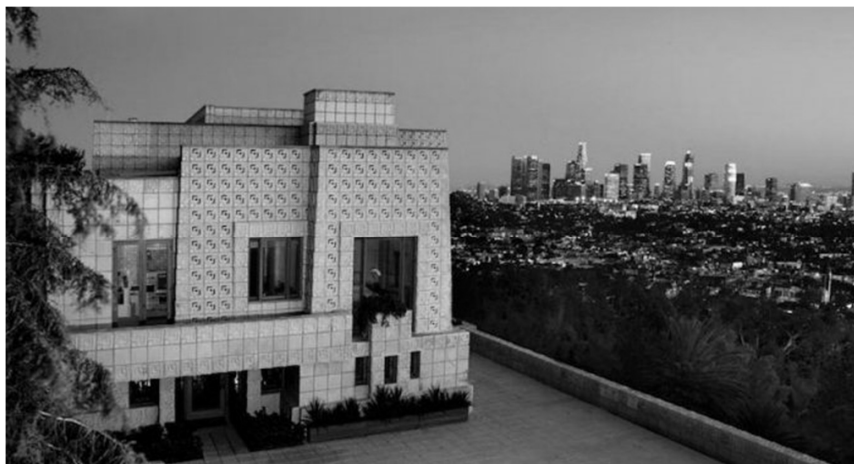

# Ennis House

- Los Angeles, Calif.
- Frank Lloyd Wright
- 1924
- Mayan Revival
- Textile Block

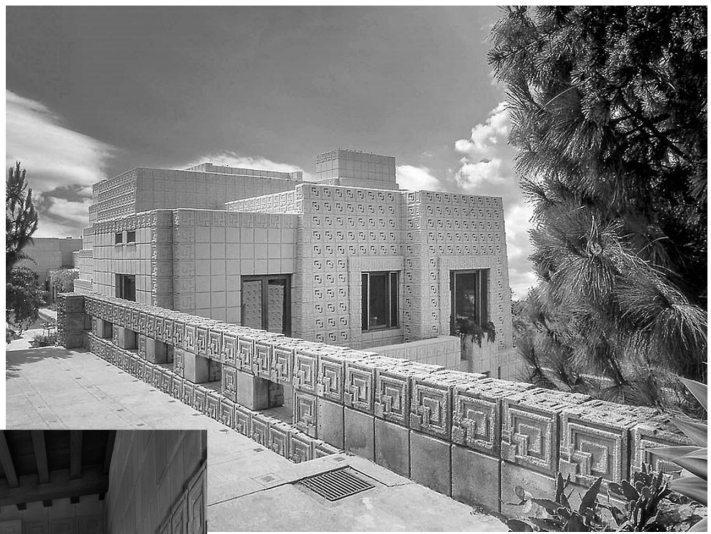

University of Michigan, TCAUP


Masonry

Slide 3 of 33

# Concrete Masonry Units

## Nomenclature

- Solid < 25% void    Hollow > 25% void
- Net area is minus the voids
- Most are hollow – 50% to 60%
- Core is a void < 1.5 inches
- Frog is a depression
- Ears are extensions at ends

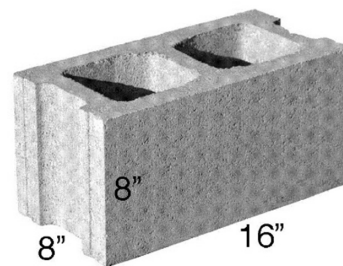

## Sizes

- 8 inch grid
- 3/8 inch mortar joint


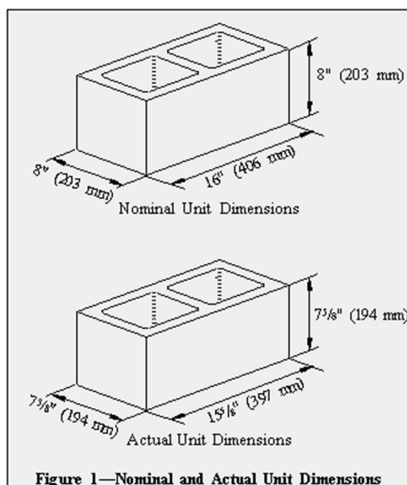


Figure 1—Nominal and Actual Unit Dimensions

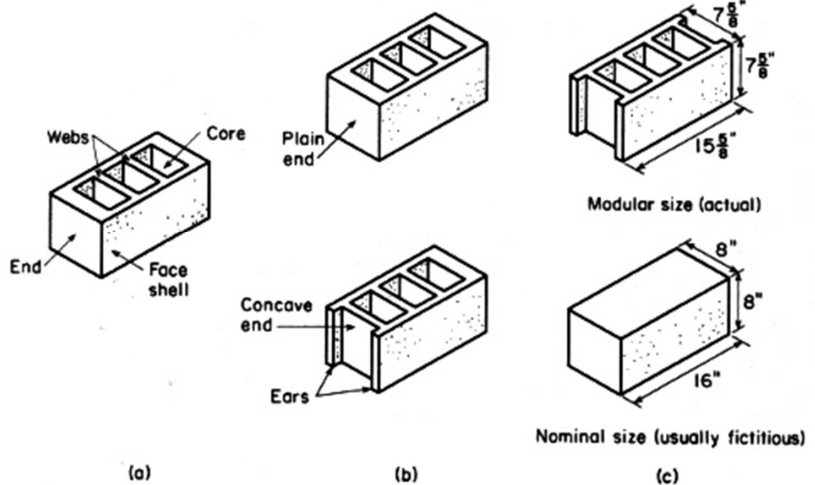

University of Michigan, TCAUP

Masonry

Slide 4 of 33

# Concrete Masonry Units (CMU)



# Concrete Masonry Units (CMU)

- Cast (molds)
- Dried
- Autoclaved


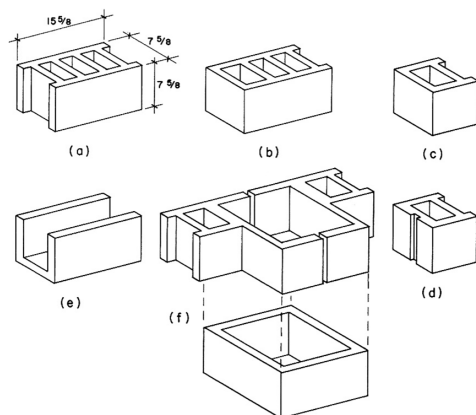


FIGURE 5.1. Forms of CMUs for unreinforced construction.

## 1.9.1 Standard Concrete Masonry Unit (CMU) Stretchers and Unit Coring


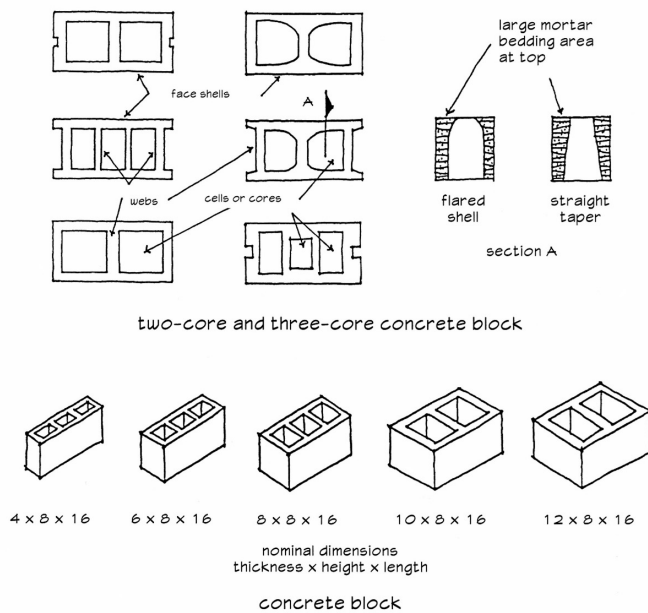


# Concrete Masonry Units

## Nomenclature

### Sizes

- 8 inch grid
- 3/8 inch mortar joint

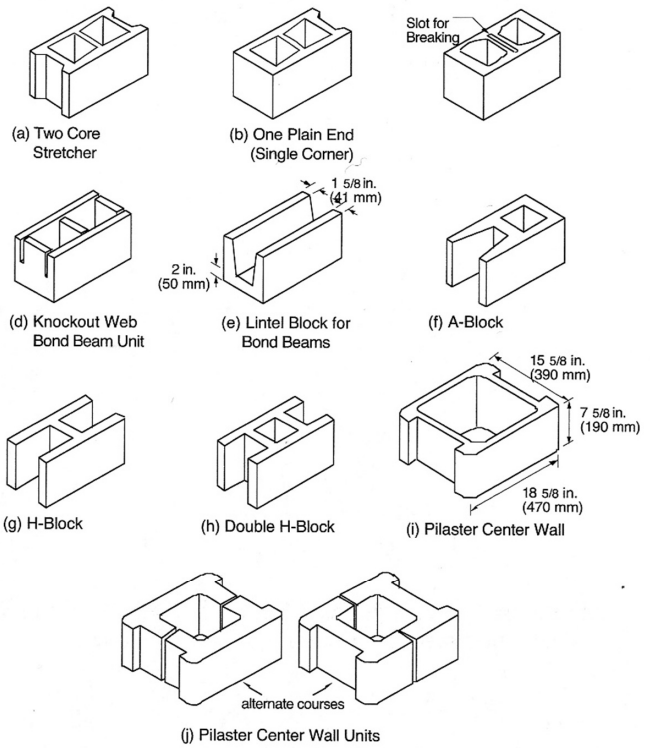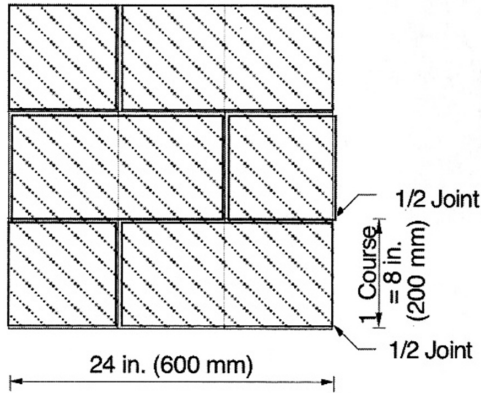

Note that (a) to (i) are shown in the 8 x 8 x 16 in. (200 x 200 x 400 mm) standard block size but other standard widths are available. Half block heights and other heights can be obtained.



Figure 4.23 Typical concrete masonry units.

# Concrete Masonry Units – CMU

## Nomenclature

### Sizes

- 8 inch grid
- 3/8 inch mortar joint

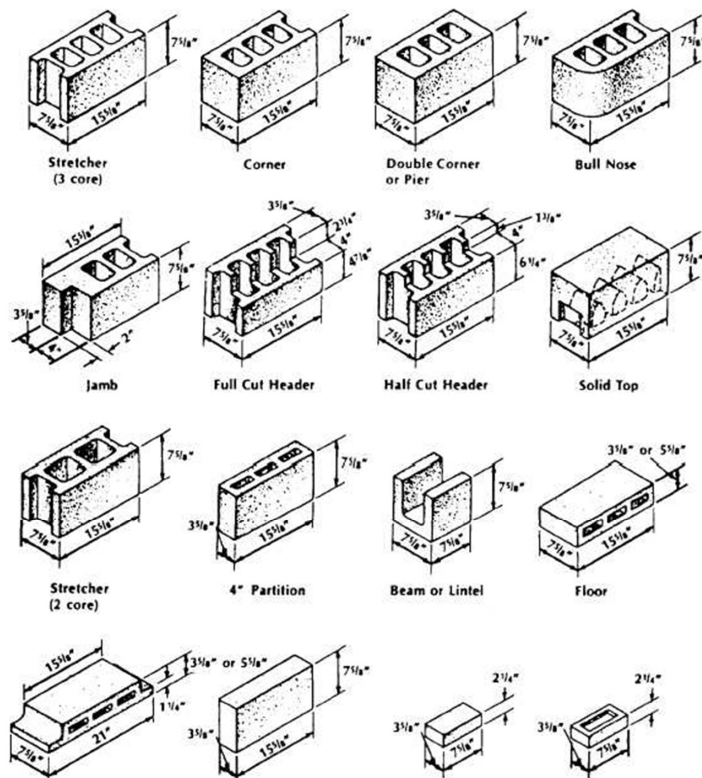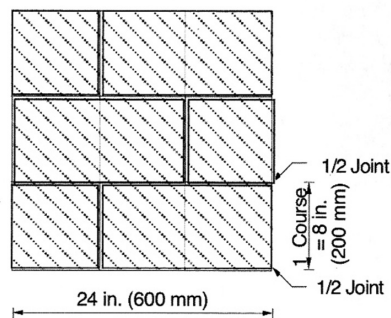

# Concrete Masonry Units – CMU

## Making a Bond Beam




## CMU

### Nomenclature

### Sizes

- 8 inch grid
- 3/8 inch mortar joint

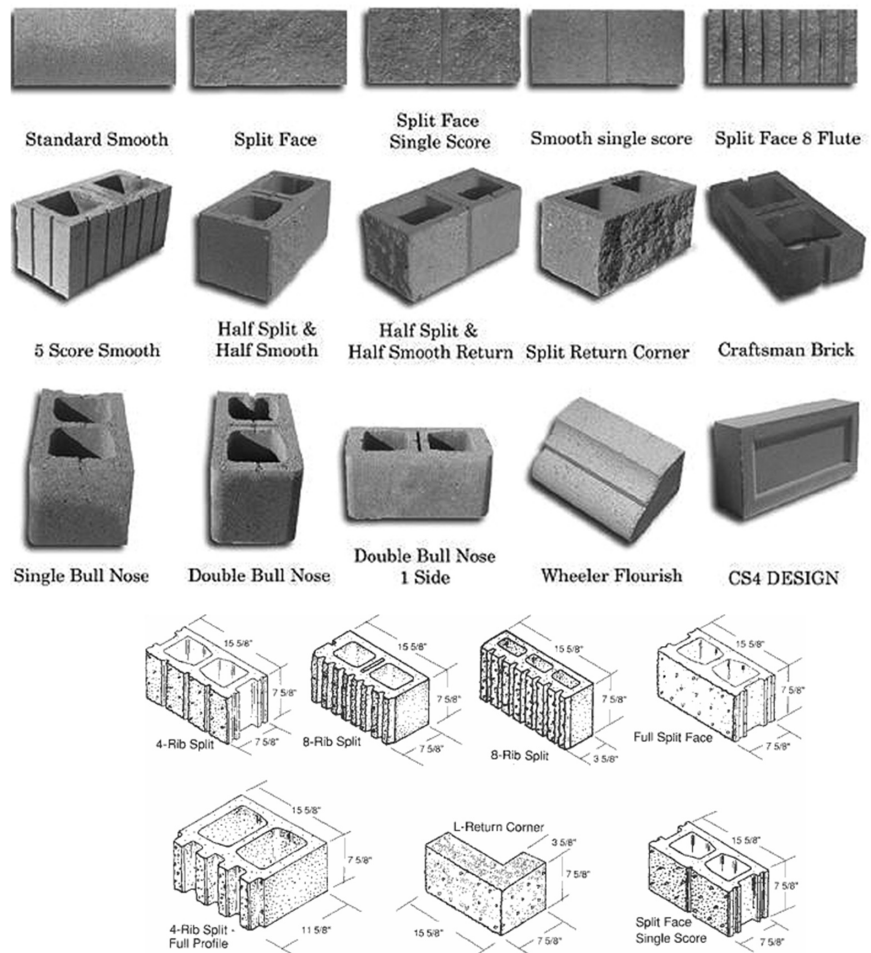


# Concrete Masonry Units (CMU)

- Reinforcing

## Joint Reinforcing



Truss Type



Ladder Type


Horizontal reinforcement required for masonry not laid in running bond of  $0.00028A_g$ , placed at a maximum spacing of 48 in. o.c. in horizontal mortar joints or in bond beams.

$$0.00028(7.625)(16) = 0.034\text{in}^2 \quad \text{Use 9 gage (W1.7) at 16 in. o.c.}$$

## Rebar Positioners



Placed in mortar joints



Concrete Masonry Units




Placed in cells




# Concrete Units – Manufacture

## Ingredients

- Portland cement
- aggregate
- Water
- Blast furnace slag
- Fly ash
- Air entrainment
- Workability
- color

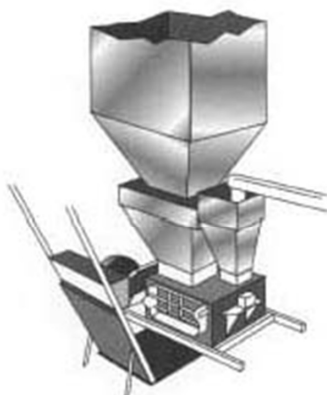

The weigh batcher is used to measure the proper amounts of each material.

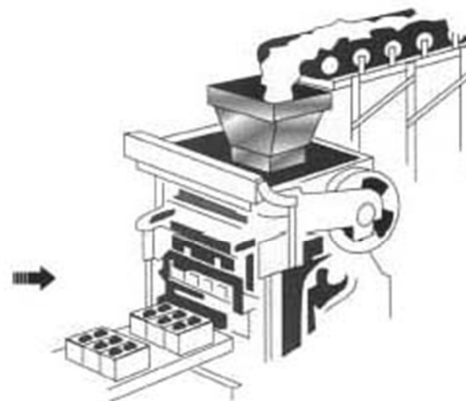

The concrete comes off a conveyor and is forced into molds. The rotating brushes remove loose material.

# CMU – Manufacture

## Molding

- Zero slump
- Press molded
- Vibrated
- Steel molds – tapered for release
- 2000 units per hour

## Curing

- Steam autoclave – 18 hrs


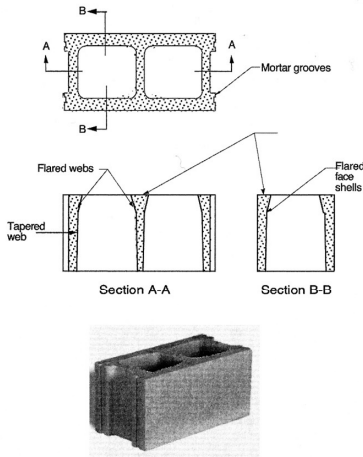


Figure 4.22 Variation in cell pattern and cell shape for a standard block. (Note the presence of taper and possible flare).

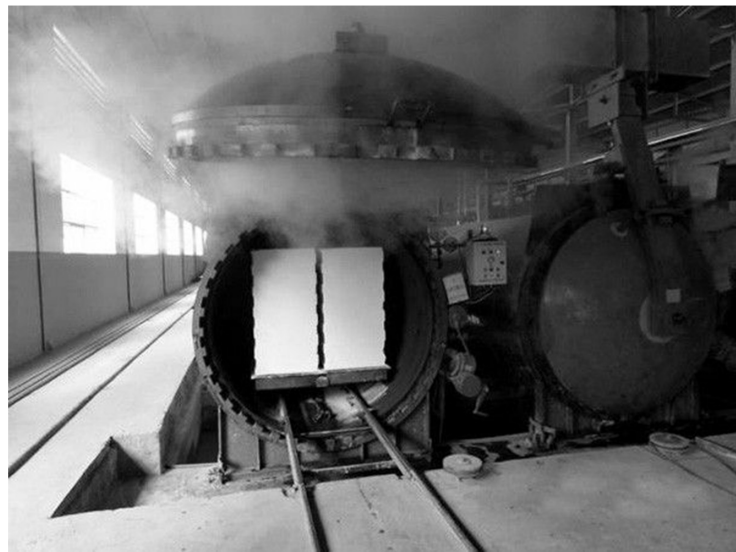

# CMU – Strength

## Classification

- Load bearing - CMU
- Non-loadbearing – facing
- Strength 2000 to 4000 psi

## Tensile strength

- Modulus of rupture or split
- 10% to 20% of compression

## Absorption lb/ft<sup>3</sup>

- Related to durability
- And shrinkage
- 24 hour immersion
- No IRA test
- 3 unit average
- Individual

Table 4.3 Strength and Absorption Requirements for Concrete Masonry Units (ASTM C90 Standard)

Weight classification	Oven-dry density of concrete, lb/ft <sup>3</sup> (kg/m <sup>3</sup> ) Average of 3 units	Maximum water absorption, lb/ft <sup>3</sup> (kg/m <sup>3</sup> )		Minimum net area compressive strength, psi (MPa)	
		Average of 3 units	Individual unit	Average of 3 units	Individual unit
Lightweight	Less than 105 (1,680)	18 (288)	20 (320)	2,000 (13.8)	1,800 (12.4)
Medium weight	105 to less than 125 (1,680 - 2,000)	15 (240)	17 (272)	2,000 (13.8)	1,800 (12.4)
Normal weight	125 (2,000) or more	13 (208)	15 (240)	2,000 (13.8)	1,800 (12.4)

Table 4.4 Strength and Absorption Requirements for Concrete Facing brick (ASTM C1634 Standard)

Density classification	Oven-dry density of concrete, lb/ft <sup>3</sup> (kg/m <sup>3</sup> ) Average of 3 units	Maximum water absorption, lb/ft <sup>3</sup> (kg/m <sup>3</sup> )		Minimum net area compressive strength, psi (MPa)	
		Average of 3 units	Individual unit	Average of 3 units	Individual units
Lightweight	Less than 105 (1,680)	15 (240)	17 (272)	3,500 (24.1)	3,000 (20.7)
Medium weight	105 to less than 125 (1,680 - 2,000)	13 (208)	15 (240)	3,500 (24.1)	3,000 (20.7)
Normal weight	125 (2,000) or more	10 (160)	12 (192)	3,500 (24.1)	3,000 (20.7)

# CMU – Performance

## Durability

- Higher strength
- Lower absorption

## Expansion

- $5 \times 10^{-6} / ^\circ F$  (normal weight)
- $4 \times 10^{-6} / ^\circ F$  (lightweight)

## Shrinkage


- Like cement
- Drying shrinkage – loss of water. Will regain if water is added, therefore usually not wet before use.
- Carbonation shrinkage – due to hydration over time – not reversible

## Creep

- A bit less than concrete
- Lightweight CMU more than normal
- Mostly within the first year

Table 4.5 Typical Shrinkage of Concrete Masonry Products.

Product	Aggregate	Curing	Total Shrinkage, %
Block	Dense gravel	Low pressure steam	0.02–0.05
	Dense gravel	Autoclave	0.01–0.04
	Lightweight	Low pressure steam	0.04–0.08
Brick	Dense	Low pressure steam	0.02–0.05

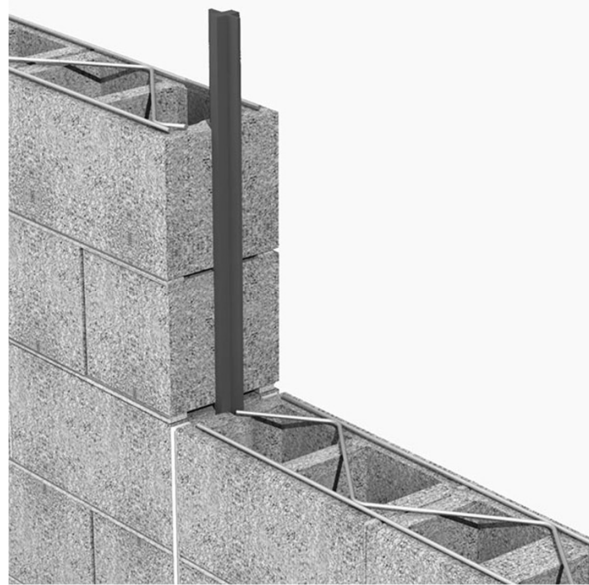

# Clay Units vs. CMU – Performance

## Typical Values

Property		Clay Masonry	Concrete Masonry
Unit strength		8000 <i>psi</i>	2000 <i>psi</i>
Type N mortar	$f'_m$	2440 <i>psi</i>	1750 <i>psi</i>
	$E_m$	$1.70 \times 10^6$ <i>psi</i>	$1.58 \times 10^6$ <i>psi</i>
Type M or S mortar	$f'_m$	2920 <i>psi</i>	2000 <i>psi</i>
	$E_m$	$2.05 \times 10^6$ <i>psi</i>	$1.80 \times 10^6$ <i>psi</i>

Property	Clay Masonry	Concrete Masonry
Modulus of Elasticity, $E_m$	$700 f'_m$	$900 f'_m$
Shear Modulus, $G$	$0.4 E_m$	$0.4 E_m$
Coefficient of Creep	$\frac{0.7 \times 10^{-7}}{\text{psi}}$	$\frac{2.5 \times 10^{-7}}{\text{psi}}$

# Calcium Silicate Units

Mainly in Europe and Australia

Formed and cured similar to CMU

- Mix of sand + hydrated lime
- Tightly grained
- Sizes follow bricks or other stone
- Generally 100% solid
- Compression by grade: 3500 to 8000 psi (or higher)

**Table 4.6** Physical Requirements for Calcium Silicate Face Brick (from Ref. 4.34).

Brick grade	Minimum compressive strength (brick tested flatwise), psi (MPa), average gross area		Water absorption maximum, lb/ft <sup>3</sup> (kg/m <sup>3</sup> )
	Average of 3	Individual	
SW	5500 (37.9)	4500 (31.0)	15 (240)
MW	3500 (24.1)	3000 (20.7)	18 (288)



Arriscraft (in US)



# Natural Stone

Mainly non-loadbearing veneer

Three basic types

- Sedimentary
- Metamorphic
- Igneous

**Table 4.7** Grouping, Common Names and Finishes of Building Stone (from Ref. 4.38).

Geological category	Common Name	Finishes
1. Sedimentary	Sandstone Limestone Dolomite	Smooth (machine finished by saw, grinder or planer) Machine tooled (with uniform grooves) Chat sawn (non-uniform) Shot sawn (irregular and uneven markings) Split face (concave-convex) Rock face (convex)
2. Metamorphic	Marble Serpentine Onyx Slate <sup>1</sup> Quartzite <sup>1</sup> Gneiss <sup>2</sup> Travertine <sup>4</sup>	Sanded Honed Polished Wheel abraded Bush-hammered Split face Rock face
3. Igneous	Granite Syenite Diorite <sup>3</sup> Gabbro Andesite Basalt	Sawn Honed Polished Machine tooled (4- or 6-cut, chiseled, axed, pointed, etc.) Flamed Sand finished Split face Rock face

<sup>1</sup> Slate and quartzite cannot be polished.

<sup>2</sup> Gneiss will take all of the finishes of marble and may also be flame finished.

<sup>3</sup> Diorite will not take flame finish.

<sup>4</sup> Travertine is actually a limestone but is classified with marbles for surface finishes. Travertine finishes include filled, partially filled, and unfilled.

# Natural Stone

Mainly non-loadbearing veneer

## Three basic types

- Sedimentary
- Metamorphic
- Igneous


**Table 4.8** Physical Requirements of Building Stone

Group of stone	Maximum absorption by weight, %	Minimum density, lb/ft <sup>3</sup> (kg/m <sup>3</sup> )	Minimum compressive strength, psi (MPa)	Minimum modulus of rupture, psi (MPa)	ASTM standard
Limestone	12	110 (1760)	1800 (12)	400 (2.9)	C568 <sup>4.39</sup>
	7.5	135 (2160)	4000 (28)	500 (3.4)	
	3	160 (2560)	8000 (55)	1000 (6.9)	
Sandstone	8	125 (2000)	4000 (27.6)	350 (2.4)	C616 <sup>4.40</sup>
	3	150 (2400)	10000 (69)	1000 (6.9)	
	1	160 (2560)	20000 (139)	2000(13.9)	
Granite	0.4	160 (2560)	19000 (131)	1500 (10.3)	C615 <sup>4.41</sup>
Marble	0.2	144 (2305) to 162 (2595)	7500 (52)	1000 (6.9)	C503 <sup>4.42</sup>

# Glass Block

## Characteristics

- Non-loadbearing
- Interior of exterior
- Reduced UV transmission
- Natural daylighting
- Solar reflection
- Fire resistance
- Thermal insulation

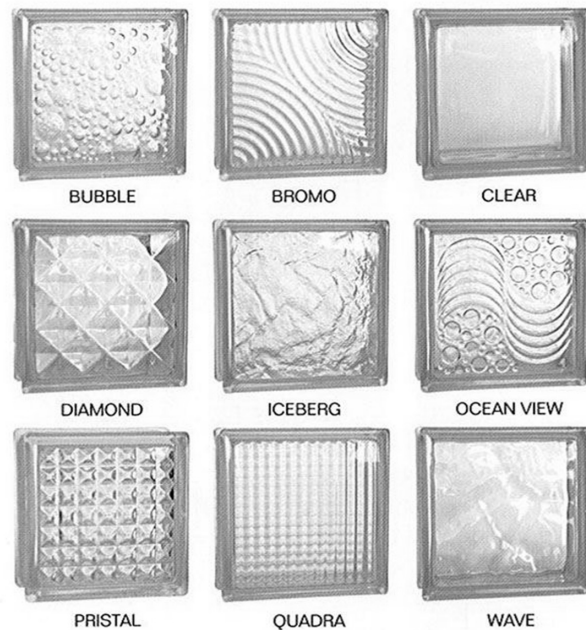


# Glass Block

## Characteristics

- Non-loadbearing
- Interior of exterior
- Reduced UV transmission
- Natural daylighting
- Solar reflection
- Fire resistance
- Thermal insulation




Ports – 1961 – Shanghai

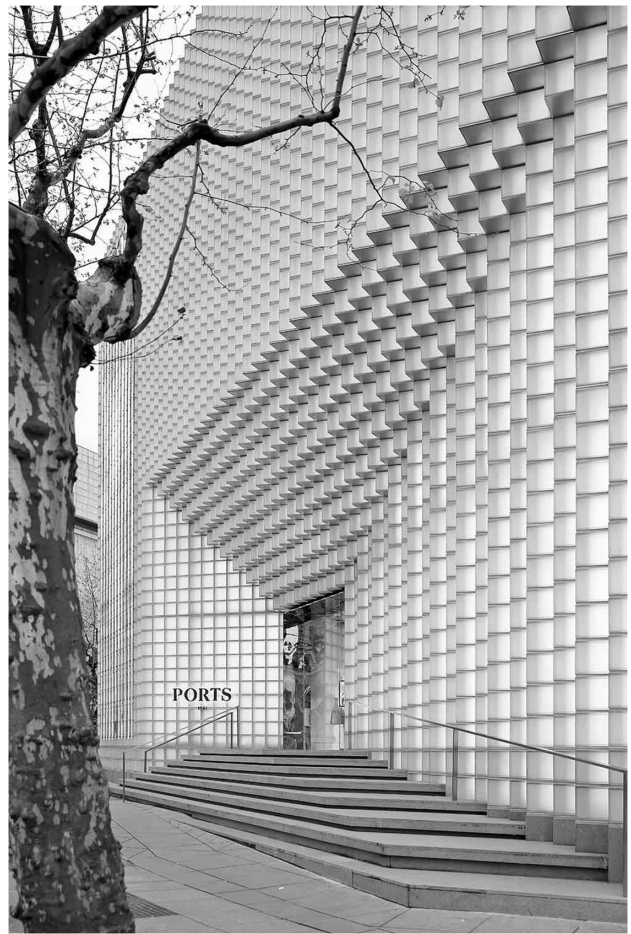


# Glass Block

- Bruno Taut
- Glass Pavilion
- Cologne Werkbund Exhibition
- 1914

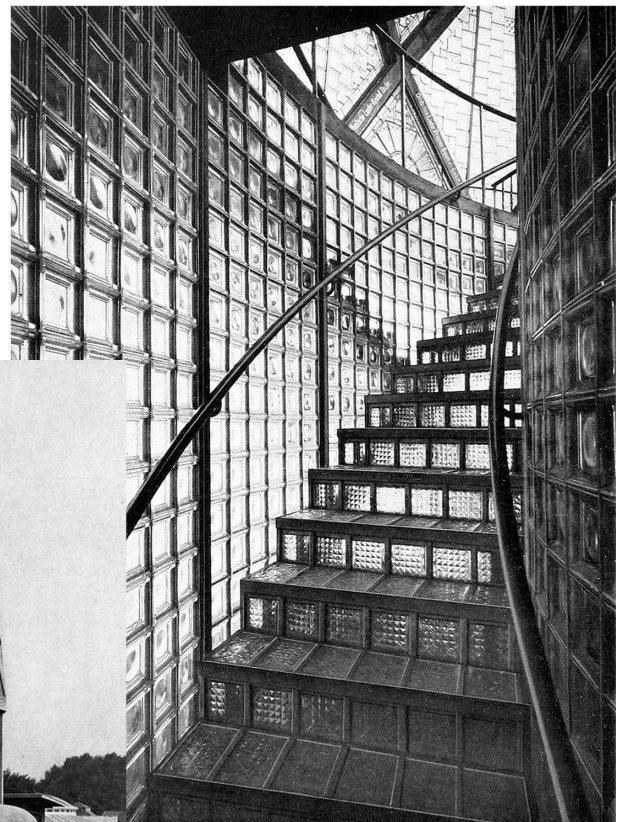

# Glass Block

- Bruno Taut
- Glass Pavilion
- 1914

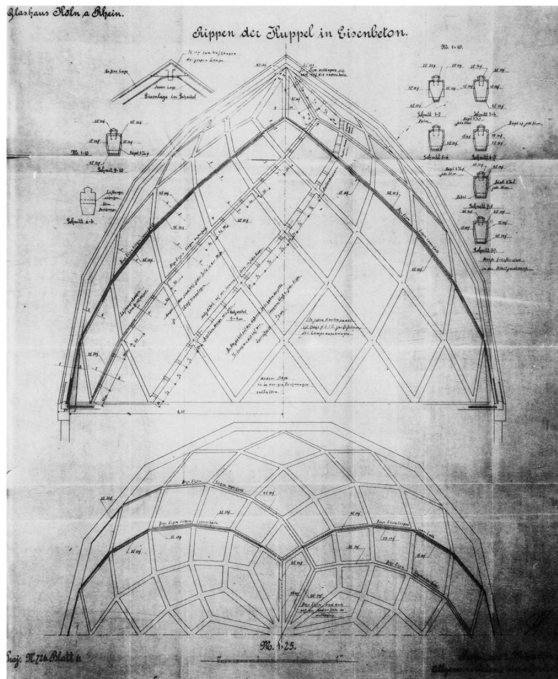

University of Michigan, TCAUP



Masonry

Slide 23 of 33

# Glass Block

Bruno Taut, Glass Pavilion, 1914





University of Michigan, TCAUP

Masonry

Slide 24 of 33

# Aerated Autoclaved Concrete – AAC

Also called:  
 Autoclaved Cellular Concrete (ACC)  
 Autoclaved Lightweight Concrete (ALC)  
 autoclaved concrete  
 cellular concrete  
 porous concrete  
 Brand names:  
 Aercon  
 Hebel Block  
 Ytong  
 Aircrete  
 Thermalite  
 Magicrete  
 BCA

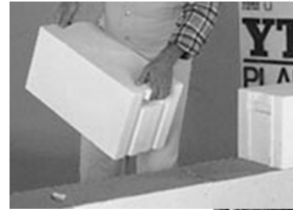
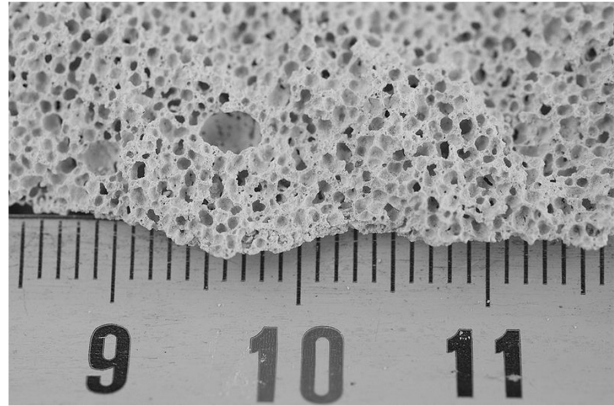


Cast and autoclaved in large slabs then cut to size  
 Lightweight, good thermal resistance,  
 transpires moisture, fireproof, sound insulation,  
 easily cut on site, erected as masonry

# Autoclaved Aeriated Concrete (AAC)

Used predominately in Europe  
 Developed by Dr. Johan Axel Eriksson in  
 mid- 1920s in Sweden as “Ytong”  
 since 1943, Hebel blocks in Germany  
 Current largest production in China

Lighter weight  
 Better insulation value  
 Better fire resistance  
 Better moisture transmission  
 Larger blocks for faster erection  
 Can be shaped on site

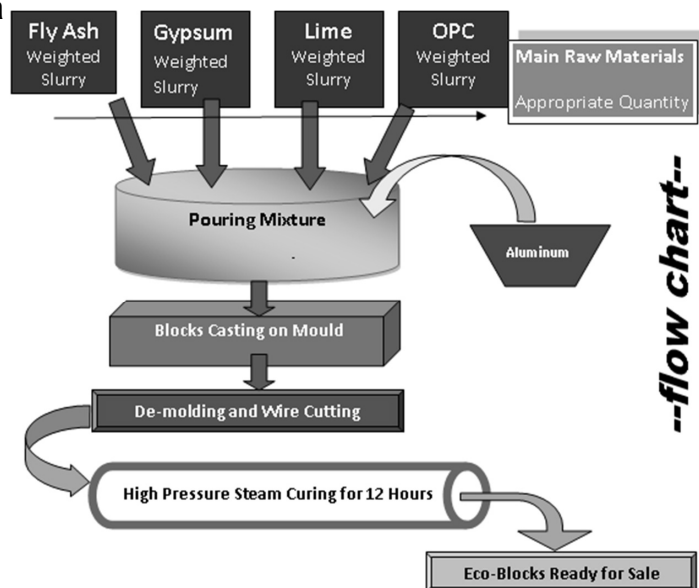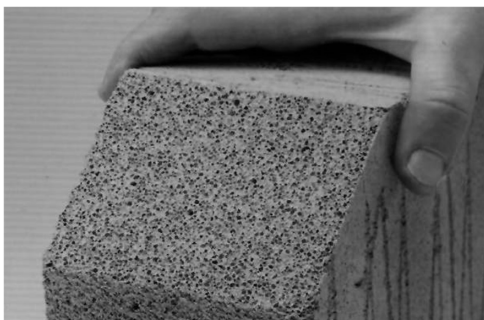

**--flow chart--**

# AAC - Aircrete






## Autoclaved Aeriated Concrete (AAC)

Density – 20 to 50 PCF (floats)

Compressive strength – 300 to 900 PSI

Allowable Shear Stress – 8 to 22 PSI

Thermal Resistance - 0.8 to 1.25 R/ IN

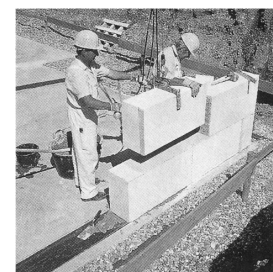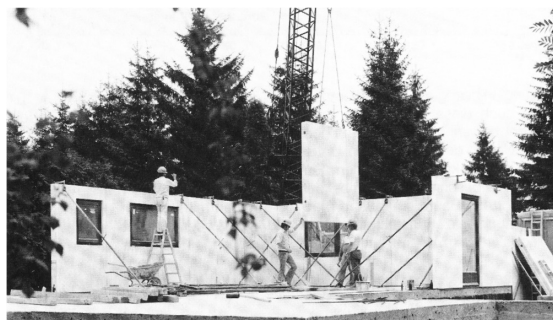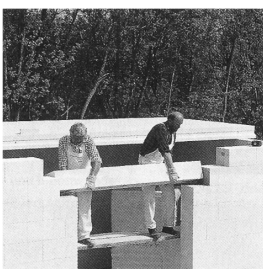

# AAC Units

'Porenbeton'

Dimensions	Standard (In)	Semi-Jumbo (In)	Jumbo (In)	O-Block (In)	U-Block (In)
Length	24	24	39-3/8	24	24
Height	8	16	24	8	8
Thickness	4 to 12	6 to 12	6 to 12	6 to 12	6 to 12
Class	AAC-2 and AAC-4			AAC-2	
Thicknesses	4, 5, 6, 7, 8, 10 and 12 In				









## Autoclaved Aeriated Concrete (AAC)

Easily shaped on site

Thin mortar bed – 1/8" (1mm to 3mm)

Tools for placement (below)

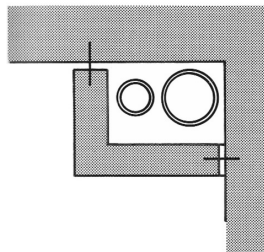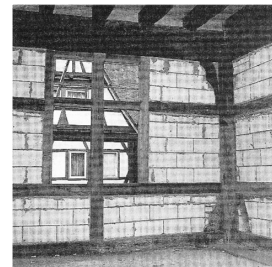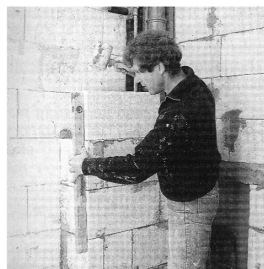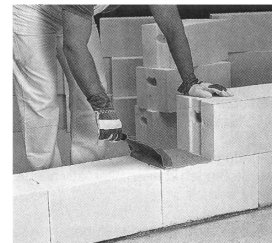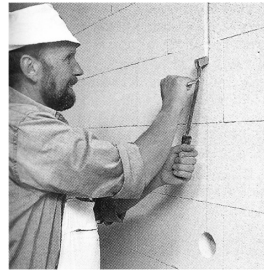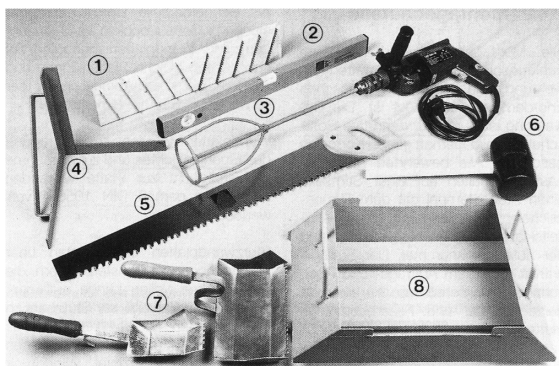




# AAC Construction



## Autoclaved Aeriated Concrete (AAC)


Larger blocks so faster layup – e.g. 8”x8”x24”

Panel layup with onsite crane

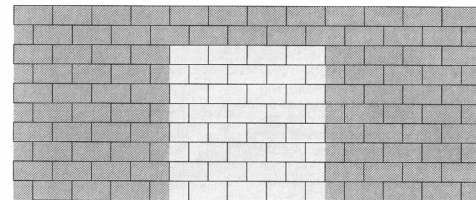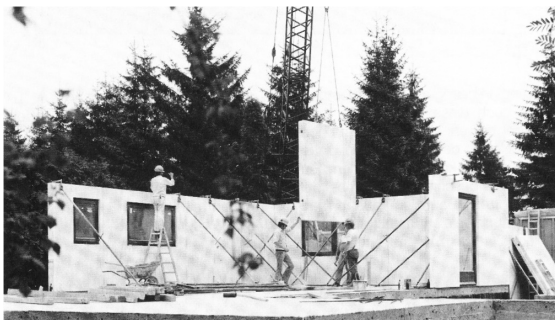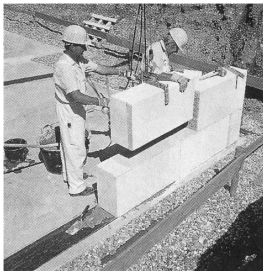


Clay block  
32 blocks / m<sup>2</sup>  
9.4" x 4.4"

Konventionelles Mauerwerk:  
32 Steine 2 DF/3 DF für 1 m<sup>2</sup> Wand;  
Steinmaß 240 mm x 113 mm x d

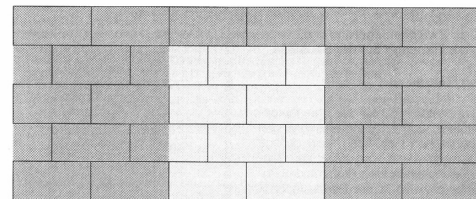

AAC block  
8 blocks / m<sup>2</sup>  
19.6" x 9.8"

Porenbeton-Plansteine:  
8 Steine pro 1 m<sup>2</sup> Wand;  
Steinmaß 499 mm x 249 mm x d

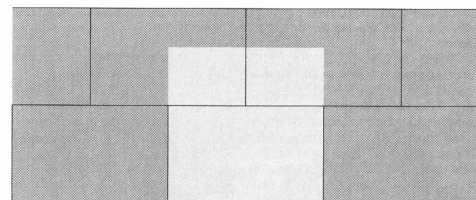

AAC panel  
1.6 panels / m<sup>2</sup>  
39.3" x 24.5"

Porenbeton-Planellemente:  
1,6 Steine pro 1 m<sup>2</sup> Wand;  
Steinmaß 999 mm x 623 mm x d

# Autoclaved Aeriated Concrete (AAC)

## Finish with stucco

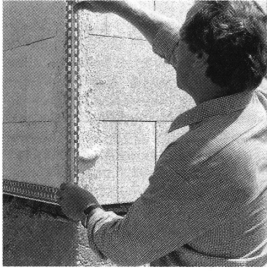


Abb. 2.4.4-1  
**Anbringen der Sockelabschluß- und Eckschutzschiene zur Sicherung der Mauerwerkskanten**



Abb. 2.4.4-2  
**Auftrag des Grundputzes von Hand**

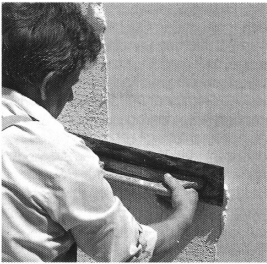


Abb. 2.4.4-3  
**Auftrag der Deckschicht**

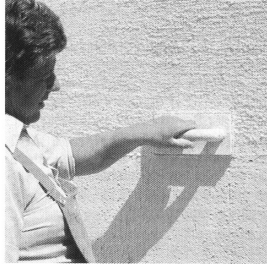


Abb. 2.4.4-4  
**Verreiben der Putzoberfläche mit Filzbrett oder Schwammscheibe**

